

**POLTRACK SANDWICH SYSTEM**  
**Running track spike-proof system**  
**Certified by WORLD ATHLETICS former I.A.A.F.**



**Synthetic outdoor system for running tracks.** It is applied on fine asphalt or smooth, waterproof concrete, without rising humidity issues, beginning with the first layer (base layer) mixed at site, which consists of **RECYCLED RUBBER 858** and the polyurethane binder **POLAPLAST P13**. The second layer (sealing layer) is the colored polyurethane sealing material **POLAPLAST P22** on top of the cushion mixture and the third layer (surface layer) is the full – PU colored polyurethane material **POLAPLAST P20**, before broadcasting EPDM granules on top to finish it off. Priming with POLAPLAST P10 precedes the application.

**Steps :**

1. **POLAPLAST P10 - Polyurethane primer.**
2. **Mixture of POLAPLAST P13 and RECYCLED RUBBER 858, applied by paving machine.**
3. **Application of POLAPLAST P22-sealing layer.**
4. **Application of POLAPLAST P20 top layer.**
5. **Broadcasting of EPDM granules.**

## Preparation – Application

Applied on dry asphalt surfaces (30 days old at least) or smooth concrete surfaces (30 days at least old) without arising humidity issues and free of materials that might prevent bonding e.g. dust, loose particles etc (in case of asphalt or concrete). The success in the application depends on the right preparation of the underlay and use of the material.

- **Good, dry cleaning** of the surface from dust and residues.
- Priming of the surface **with POLAPLAST P10** applied by airless spray or brushes. The base coat of **POLTRACK SYSTEM** should be constructed while **POLAPLAST P10** is still sticky (wet on wet procedure).
- The base shock-absorbent layer OF **POLTRACK SYSTEM** should be constructed within 6-12 hours of primer application.
- **Good mixing of the POLAPLAST P13 with recycled rubber granules** (1-4mm) to create a flexible shock-absorbent layer.
- The mixture is poured on the surface and spread using a suitable paving machine or other appropriate machine or a hand straightedge. If the application will be done with hand straightedge then small irregularities in the surface may be removed by rolling on the fresh surface using a metallic cylinder.
- After the surface is fully cured (depending on the temperature and humidity, the curing of the shock-pad cushion base coat of **POLTRACK** will take 12-48 hours), follows the application of PU pore filler **POLAPLAST P22** in 2 crossing layers with a trowel. Any irregularities from application must be removed from the use of sandpaper machine generally or on the spot. Consumption: 2kg/m<sup>2</sup> for two layers.
- The top coating of the **POLTRACK SANDWICH SYSTEM** is applied in one layer by flat metal trowel of the material **POLAPLAST P20**. Then on the wet fresh PU self leveling surface follows the broadcasting of the EPDM granules (granulometry 1-3mm) with consumption 3,6 - 4 kg /m<sup>2</sup>.
- After the top layer has cured (depending on conditions, this will usually take 9-12 hours at 20°C), it can be walked on. After 2 days, the top coating of **POLTRACK SANDWICH SYSTEM** is fully cured and can be put into service, after proper line marking is performed with the use of special two component polyurethane paint.

## Important Remarks

- ✓ During temperatures over 40 degrees, ideal time for the application of **POLTRACK SANDWICH SYSTEM** is between 22:00 and 09:00. The minimum bearing temperature during application and drying should be over 10°C.
- ✓ The freshly coated surface should be protected from high temperatures, wind, rain and frost for at least the first 24 hours.

## Substrate

**Asphalt is the safer subfloor for sport floorings for sure and must be always preferred than concrete surfaces.**


### **A. Asphalt Substrate**

**The asphalt must have a slope of 0.7-1% and must dry for at least 30 days so that all solvents from the asphalt can evaporate.**

The asphalt sub-floor should be applied on well compacted 150mm road base sub-floor and asphalt should be laid in one layer (and not 2) in 6 to 8cm with fine and coarse aggregates (up to 15mm granulometry) like the kind of asphalt used in road construction.

So, new road-grade asphalt will have to be laid (minimum 60mm) in one layer containing coarse aggregates and then mature for 30 days at least, before any application takes place on top of the asphalt to avoid bubbles on the final layer of the sport or rubber floorings.

## Asphalt Infrastructure

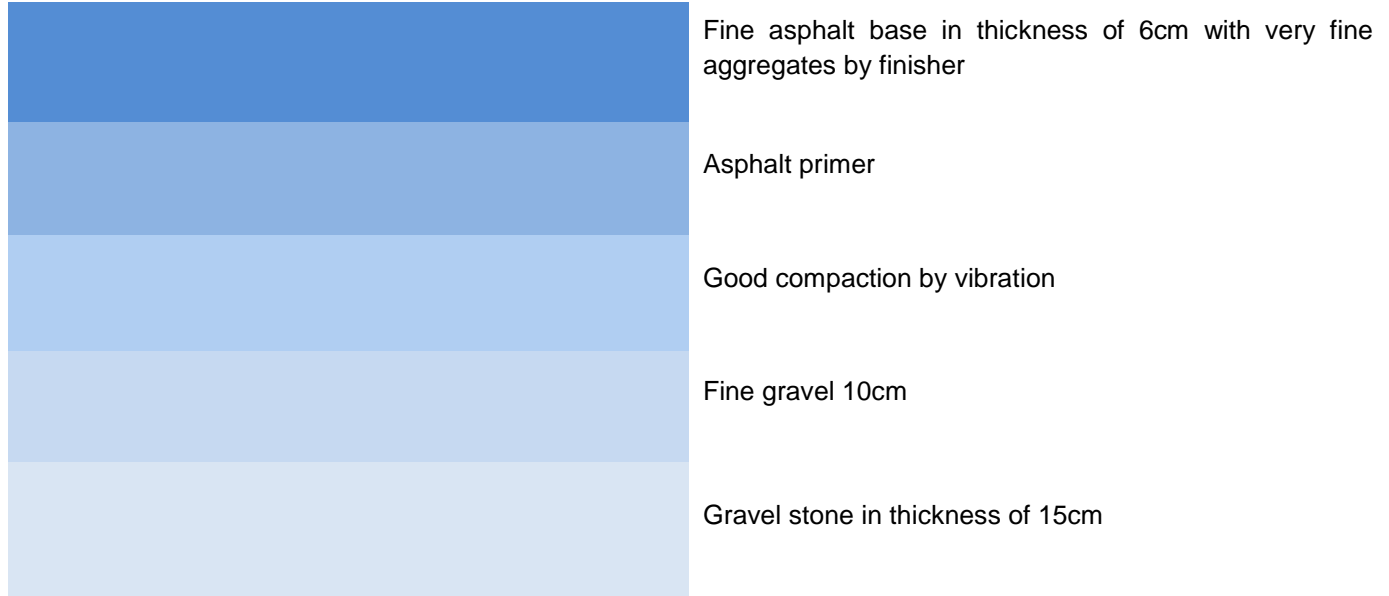


### B. Concrete Surface

**Concrete surface must be power-trowelled without cracks and must be smooth with a slope of 0.7-1% and humidity under 4% in 10cm depth of concrete.**

Concrete must also be **dry at least for 40 days** and then the application takes place if there is no rising humidity for the sub-floor. Before the application takes place, there must be proper grinding of the surface by a grinding machine to open the pores accordingly and also a measurement by special instrument to measure humidity on the surface and in 10cm under the surface.

Generally concrete is a risky sub-floor and there may be problems with rising humidity, especially in areas where the sea level is really high and when the sea is close or in areas near greenery.

**Always make expansion joints in large areas of concrete, in order to avoid uncontrollable cracks and failures.** Joints should be every 25 square meters creating a grid of 5x5 meters or close to that.

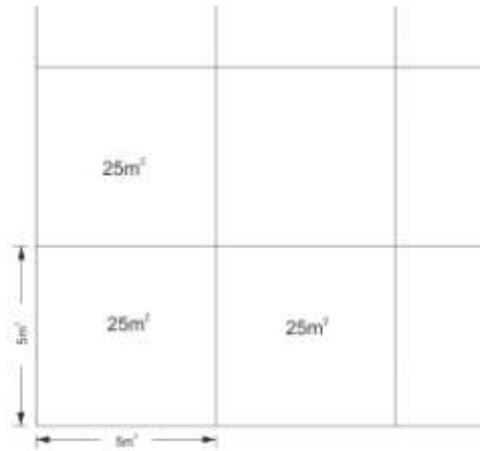

<b><u>SUBSTRATE REQUIREMENTS</u></b>	Concrete quality	at least C20/25
	Age:	at least 40 days
	Moisture content:	below 4%

**Tools:**



**AIRLESS SPRAYER**



**BRUSH**



**PAVING MACHINE**



**STRAIGHTEDGE**



**RAKE**

**KDF - Kataskeves Dapedon LTD**  
 e : [exports@kdf.gr](mailto:exports@kdf.gr) w : [www.kdf.gr](http://www.kdf.gr)

**Showroom Office**  
 1 Papanikolaou Ave, Pefka  
 57010, Thessaloniki, Greece  
 t / f : 0030 2310 829598

**Accounting Office**  
 19 Mitropoleos Str  
 54624, Thessaloniki, Greece



# KDF

Sports Flooring Systems & Building Materials  
50 YEARS OF EXPERIENCE



This is a certified system by WORLD ATHLETICS former I.A.A.F.

**KDF - Kataskeves Dapedon LTD**  
e : [exports@kdf.gr](mailto:exports@kdf.gr) w : [www.kdf.gr](http://www.kdf.gr)

**Showroom Office**  
1 Papanikolaou Ave, Pefka  
57010, Thessaloniki, Greece  
t / f : 0030 2310 829598

**Accounting Office**  
19 Mitropoleos Str  
54624, Thessaloniki, Greece



International Association of Athletics Federations



## Product Certificate

The IAAF is pleased to certify hereby that the following product:

**Product's Trade Name:** Synthetic surface, Poltrack Sandwich  
**Description, Colour / Absolute Thickness:** Sandwich, 15.5mm  
**Company Name, Country:** Kataskeves Dapedon Ltd. (KDF), GRE  
**Catalogue Number:** -  
**IAAF Certification Number:** S-18-0228

has been tested and meets the technical requirements for use in all international athletics competitions.  
**Test Report: No. 160200546-2, 9 December 2016, Kiwa ISA Sport (NED)**

**Valid from:** 1 January 2018  
**Until the last day of:** January 2022

This certificate is issued in accordance with the terms and conditions of the IAAF Certification System of track and field facilities, implements and competition equipment.

SEBASTIAN COE  
IAAF President

JORGE SALCEDO  
IAAF Technical Committee Chairman



KDF - Kataskeves Dapedon LTD  
e : exports@kdf.gr w : www.kdf.gr

**Showroom Office**  
1 Papanikolaou Ave, Pefka  
57010, Thessaloniki, Greece  
t / f : 0030 2310 829598

**Accounting Office**  
19 Mitropoleos Str  
54624, Thessaloniki, Greece



LABOSPORT

# KDF

Sports Flooring Systems & Building Materials  
**50 YEARS OF EXPERIENCE**

**TÜV HELLAS**  
TÜV NORD GROUP

## CERTIFICATE

Management system as per  
**ISO 9001 : 2015**  
**Quality Management Systems-Requirements**

In accordance with TÜV HELLAS (TÜV NORD) S.A., procedures, it is hereby certified that

**KATASKEVES DAPEDON L.T.D.**  
Head Quarters: 19, Mitropoleos Str.  
546 24 Thessaloniki  
Branch: Lakkoma  
630 80 Chalkidiki  
Hellas

**KDF**  
Sports Flooring Systems & Building Materials  
**45 YEARS OF EXPERIENCE**

applies a management system in line with the above standard for the following scope

**Production and Sale of Sports Flooring Systems.**

Certificate Registration No. 041 17 0182  
Audit Report No. E-2997/2018

Valid from 2017-12-20  
Valid until 2020-12-19  
Initial certification 2017

*3Katala/w*

TÜV HELLAS (TÜV NORD) S.A. Certification Body  
Athens, 2018-10-20

This certification was conducted in accordance with the TÜV HELLAS (TÜV NORD) S.A. auditing and certification procedures and is subject to regular surveillance audits.



MS Certifications  
No. of certificate 100



TÜV HELLAS S.A. 282, Mesogeion Ave., 155 62 Cholargos, Athens, Greece

**KDF - Kataskeves Dapedon LTD**  
e : [exports@kdf.gr](mailto:exports@kdf.gr) w : [www.kdf.gr](http://www.kdf.gr)



**Showroom Office**  
1 Papanikolaou Ave, Pefka  
57010, Thessaloniki, Greece  
t / f : 0030 2310 829598  
**Accounting Office**  
19 Mitropoleos Str  
54624, Thessaloniki, Greece